


Meas.Nr. 62277 **Date** Montag, 18 März 2013 02:30 **Personal Report No.:**
Material Cement (in IPA) 60min P6cl 250ml WC 5mm **M130049**
Description predisp. in water with 0,1% Na4P2O7 1min ultrasonic LABORETTE 17

Calculation Fraunhofer broad **TradeOff** 1.000000e+003
Scans Fine 100 **Scans Coarse** 100 **Channels** 102 **Beam Obscuration** 14.00 %
Meas. Range 0.08 [µm] - 2000.00 [µm] **Pump** 7 **Ultrasonics** 10

%	< µm
5	0.51
10	0.69
15	0.85
20	1.00
25	1.16
30	1.32
40	1.67
50	2.09
60	2.62
70	3.39
80	4.72
90	9.20
95	14.86
98	20.16
99	23.20

%	< µm
0.2	0.1
4.9	0.5
12.0	0.8
20.0	1.0
65.5	3.0
81.3	5.0
88.5	8.0
90.8	10.0
95.1	15.0
97.9	20.0
99.4	25.0
99.9	30.0
100.0	35.0
100.0	40.0
100.0	50.0

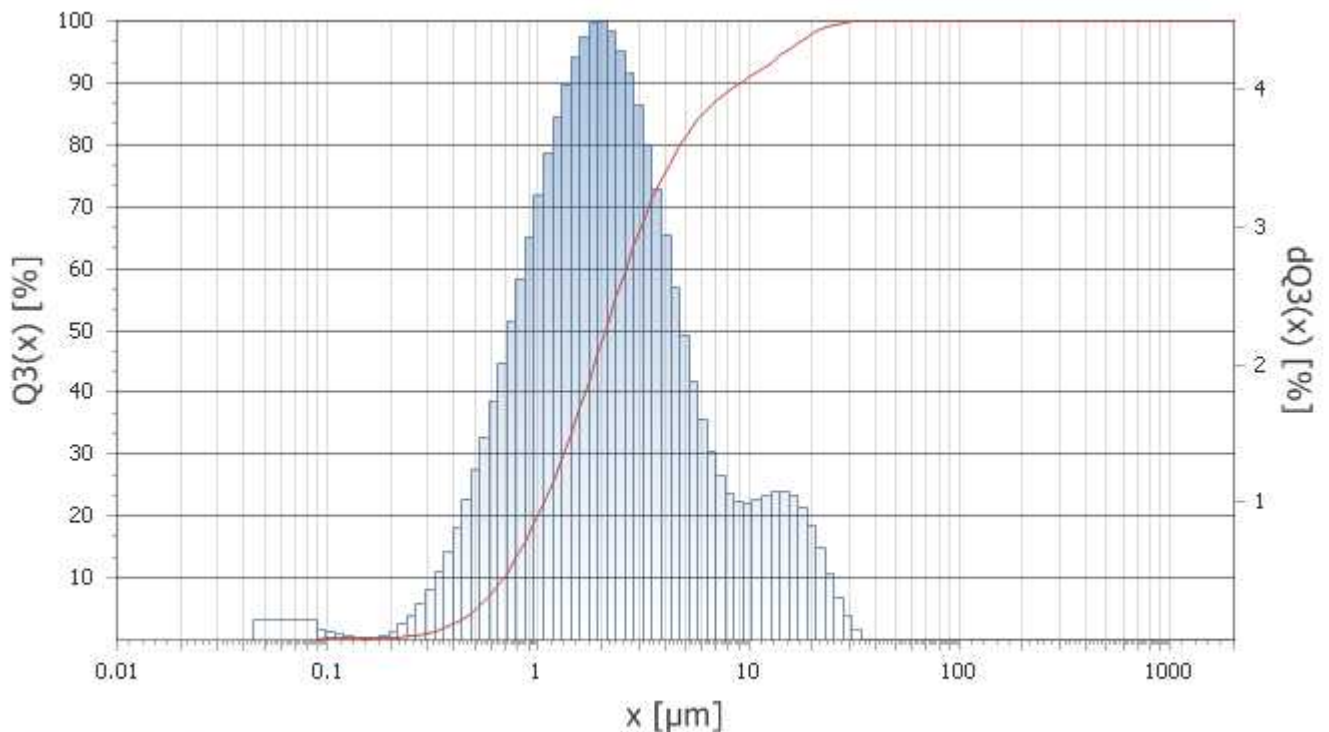

▲ 62277 dQ3(x) — 62277 Q3(x)